

EDITORIAL BOARD

ESTEEM ACADEMIC JOURNAL

VOLUME 11, NUMBER 1, JUNE 2015

Universiti Teknologi MARA (Pulau Pinang)

ENGINEERING, SCIENCE & TECHNOLOGY

ADVISORS

Tan Sri Prof. Ir. Dr. Sahol Hamid Bin Abu Bakar, FASc

Assoc. Prof. Dr. Ngah Ramzi Hamzah

PANEL OF REVIEWERS

Prof. Dr. Hj. Ismail Abustan (*Universiti Sains Malaysia*)

Assoc. Prof. Dr. Poh Beng Teik (*Universiti Sains Malaysia*)

Assist. Prof. Dr. Chan Swee Huat (*University of Nottingham Malaysia*)

Dr Mohd Firdaus Yhaya (*Universiti Sains Malaysia*)

Dr Wong Kwong Soon (*Curtin University, Sarawak Malaysia*)

Dr. Azli Yahya (*Universiti Teknologi Malaysia*)

Dr. Azmi Bin Mohamed Yusof (*Universiti Teknologi MARA (Pulau Pinang)*)

Dr. Charles Loo Chin Moy (*Curtin University, Sarawak Malaysia*)

Dr. Ching Yern Chee (*University of Malaya*)

Dr. Effarizah Mohd Esah (*Universiti Sains Malaysia*)

Dr. Eileen Su Lee Ming (*Universiti Teknologi Malaysia*)

Dr. Haidi Ibrahim (*Universiti Sains Malaysia*)

Dr. Lyly Nyl Ismail (*Universiti Teknologi MARA (Pulau Pinang)*)

Dr. Mohammad Nizam Ibrahim (*Universiti Teknologi MARA (Pulau Pinang)*)

Dr. Mohd Sayuti Ab Karim (*University of Malaya*)

Dr. Nor Fazila Che Mat (*Universiti Sains Malaysia*)

Dr. Ong Hwai Chyuan (*University of Malaya*)

CHIEF EDITOR

Dr. Chang Siu Hua

MANAGING EDITOR

Dr. Maryam Farooqui

TECHNICAL EDITORS

Dr. Ong Jiunn Chit

Sundara Rajan Mahalingam

LANGUAGE EDITORS

Muriatul Khusmah Musa (*Universiti Teknologi MARA (Pulau Pinang)*)













Rasaya A/L Marimuthu (*Universiti Teknologi MARA (Pulau Pinang)*)

FOREWORD

First and foremost, we would like to extend our sincere appreciation and utmost gratitude to Associate Professor Dr. Ngah Ramzi Hamzah, Rector of UiTM (Pulau Pinang), Dr. Mohd Mahadzir Mohammad@Mahmood, Deputy Rector of Academic Affairs and Dr. Mohd Subri Tahir, Deputy Rector of Research, Industry, Community & Alumni Network for their generous support towards the successful publication of this issue. Not to be forgotten also are the constructive and invaluable comments given by the eminent panels of external reviewers and language editors who have worked assiduously towards ensuring that all the articles published in this issue are of the highest quality. In addition, we would like to thank the authors who have submitted articles to EAJ, trusting Editor and Editorial Board and thus endorsing a new initiative and an innovative academic organ and, in doing so, encouraging many more authors to submit their manuscripts as well, knowing that they and their work will be in good hands and that their findings will be published on a short-term basis. Last but not least, a special acknowledgement is dedicated to those members of the Editorial Board who have contributed to the making of this issue and whose work has increased the quality of articles even more. Although there will always be cases in which manuscripts will be rejected, our work so far has shown that the board members' motivation has been, and will be, to make publications possible rather than to block them. By means of intensive communication with authors, academic quality is and will be guaranteed and promising research findings are and will be conveyed to the academia in a functional manner.

Dr. Chang Siu Hua
Chief Editor
ESTEEM Academic Journal
Vol. 11, No. 1 (2015)
(Engineering, Science & Technology)

CONTENTS OF JOURNAL

1. Protective Effect of Stevia Rebaudiana Leaf Extract on Hemolytic Behaviour of Human Erythrocyte in Hydrogen Peroxide-Induced Oxidative Stress 1
Norhisham Haron, Nurainah Abu Hasan, Siti Nazrina Camalxaman, Emida Mohamed, Azlin Sham Rambely and Zulkhairi Amom
 
2. Evaluation of Shear Strength Parameters Using Shear Box Tests for Slope Failures in Penang 14
Mohamad Zain Hashim, Damanhuri Jamalludin and Muhammad Hafeez Osman
 
3. Effect of Zinc Oxide on Dispersion and Homogeneity of PTFE in NR/NBR Rubber Matrices 24
Noorzalila Muhammad Niza and Buvearasan Muniandy
 
4. Obtaining the Porosity of Porous Silicon From SEM Images Based on the Image Processing Method 33
Siti Noraini Sulaiman, Nor Azilla Mohamed Shahadi, Alhan Farhanah Abd Rahim and Fadzil Ahmad
 
5. Characterization of Hydrodynamic Flow Focusing Single Particle Detection 46
Irni Hamiza Hamzah, Nurfaezah Mat Rodi, Azmi Mohamed Yusof, Ali Othman and Alhan Farhan Abd Rahim
 
6. Development of VBA for Assessment of Practical Allowable Pile Capacity 57
Mohamad Irwan P. Harahap and Muhammad Safwan bin Mohd Sobri
 

EFFECT OF ZINC OXIDE ON DISPERSION AND HOMOGENEITY OF PTFE IN NR/NBR RUBBER MATRICES

Noorzalila Muhammad Niza¹ and Buvearasan Muniandy²

¹Faculty of Chemical Engineering, Universiti Teknologi MARA Pulau Pinang, 13500, Permatang Pauh, Pulau Pinang, Malaysia

²Harvik Rubber Industries Sdn. Bhd. 1414 Lorong Perusahaan 4, (Off Jalan Perusahaan), Free Industrial Zone (1), 13600 Prai, Pulau Pinang, Malaysia

¹zalila2871@ppinang.uitm.edu.my; ²buve@harvik.com

ABSTRACT

The effect of zinc oxide (ZnO) on the dispersion and homogeneity of polytetrafluoroethylene (PTFE) in the blend of natural and nitrile rubber matrices (NR/NBR) has been investigated. The rubbers and additives were mixed on a two-roll mill and vulcanized by a steam-heated press. The findings from the chemical resistance test showed that the rubber blend with 8 parts per hundred of rubber (phr) of ZnO has better resistance towards organic solvents (acetone, heptane and toluene) and the degree of swelling reduced compared to rubber blend with lower amount of ZnO. Further investigations on the scanning electron microscopy (SEM) of the rubber compound blend with ZnO showed that the PTFE agglomerations were reduced with particle sizes ranging in the order of 2-8 μm . The decrease in the particles sizes allows an increase in the PTFE surface area with better dispersion and homogeneity in the rubber matrices to be achieved, with reduced solvent uptake by the rubber.

Keywords: Zinc Oxide; Polytetrafluoroethylene (PTFE); Natural Rubber (NR); Nitrile Rubber (NBR); dispersion; homogeneity; rubber matrices.

1. INTRODUCTION

Polytetrafluoroethylene or PTFE is well known for its high resistance to chemicals and solvents with an upper service temperature of around 260 °C (Stachowiak & Batchelor, 1993). Due to these unique properties, PTFE has been used in a wide variety of applications (Gangal, 1989). This includes the automotive applications such as seals, O-rings gaskets, etc (Drobny, 2007) and also blended with polymers or reinforced as composite materials for special applications (Morgan, Stewart, Thomas, & Stahl, 1991; Crandell, 1955; Kaufman & Gonzales, 1968). Nevertheless, its low adhesion and inert behavior restricts its dispersion and compatibility with other materials especially rubbers. Recently, newly developed PTFE micropowders have been incorporated successfully in elastomers. The modified PTFE micropowders are fine coagulated powder which are produced by emulsion polymerization and has low molecular weight commonly used as an additive in a variety of applications (Lee, Patel, Cox, & Andries, 2005; Lahijani, 2003). One of the successful studies is the blending of modified PTFE micropowders with chloroprene (CR) and ethylene-propylene-diene (EPDM)

rubbers (Khan, Lehmann, & Heinrich, 2009b; Khan, Franke, Lehmann, & Heinrich, 2009a). Khan et al. (2009a) had succeeded in producing modified PTFE micropowder which enabled this polymer to chemically couple with elastomer. Their experimental results showed that the incorporation of this modified PTFE micropowders in the rubber could improve the physical and tribological properties of the compounds, apart from enhancing the dispersion and compatibility of the PTFE micropowders in rubber matrices. A prior study in Harvik Rubber Industry on the blending of PTFE micropowder with natural rubber/nitrile (NR/NBR) rubber has showed that the PTFE micropowder was not dispersed uniformly in the rubber and the addition of homogenizing agent did not help in enhancing the homogeneity of PTFE in the rubber compound. Furthermore, PTFE micropowder tends to form clumps of particles during mixing and blending operations. The aim of the present work is to investigate the effect of the incorporation of ZnO as the activator in enhancing the dispersion and homogeneity of PTFE in rubber matrices. These PTFE-filled NR/NBR rubber blend is formulated and improvised to be used as rubber component for protection against exposure to chemicals and solvents.

2. METHODOLOGY

2.1 Materials

The grade of natural rubber used in this study was SVR 3L obtained from Hokson Rubber Trading Sdn. Bhd. This type of natural rubber is manufactured in Vietnam. Meanwhile, the type of acrylonitrile butadiene rubber or nitrile rubber used was Krynac 3330 with medium acrylonitrile (ACN) content of 33 %, viscosity ML1+4(100 °C) of 40, and specific gravity (0.98). The PTFE micropowders is Zonyl MP1100 (average particle size distribution of < 8 µm) emulsion grade which is an electron beam modified (500 kGy) PTFE micropowder produced by Dupont, Wilmington, Delaware, USA. DPG (N,N-diphenylguanidine) with specific gravity (1.19@25 °C), density (0.4 g/cm³) was used as vulcanization accelerator in rubber milling and was obtained from Hifull Chemical Industry Co Ltd, China. Sulphur (specific gravity of 2.06) and Sipernat® 820A were used as vulcanizing agent and fillers, respectively. Zinc oxide (ZnO) obtained from Metoxide Malaysia Sdn. Bhd was used as an activator to accelerate the vulcanization in compounded rubber.

2.2 Blending and Mixing

Table 1 shows the rubber compositions of each mixing. The samples were subjected to chemical degradation test to determine their resistance to selected solvents based on different polarities which were heptane, acetone and toluene. NR/NBR/PTFE blends with and without ZnO were first mixed on a two-roll mill according to the rubber blend compositions. This was followed by the addition of constant amount of additives such as fillers, accelerators, activators and vulcanizing agent into the rubber. Approximately 2 mm sheets were drawn out from the mills and the optimum cure time (t_{90}) was determined using a rotorless rheometer. The rubbers were vulcanized using a steam-heated press that was carried out at a temperature of 152 °C for 10 minutes.

2.3 Resistance to Swelling

To evaluate the chemical resistance of the samples, about 5 g of dried rubber samples were weighed and then immersed in a beaker that contained about 20 ml tested solvent for 23 hours at room temperature. The 23 hours of swelling test is in compliance with the requirement by

European Standard EN 13 832-3 ‘Requirement for boots highly resistant to chemicals under laboratory conditions’. The percentage changes in mass of the samples $Q\%$ can be calculated according to the following equation (Khalaf, Yehia, Ismail & El-Sabbagh, 2012):

$$Q\% = \frac{W_s - W_d}{W_d} \times 100 \quad (1)$$

where W_s and W_d is the weight of the swelled and the dried sample, respectively.

Table 1: Rubber blends compositions.

	Rubber and additives compositions (phr)			
	1	2	3	4
NR	40	40	40	40
NBR	60	60	60	60
PTFE Micropowder	30	30	30	30
ZnO	-	3	5	8

2.4 Microstructural Analysis by SEM/EDX

The microstructural analysis was carried out using Scanning electron microscopy (SEM) and energy dispersive x-ray spectroscopy (EDX) to compare the effect of ZnO on the rubber matrices in NR/NBR/PTFE compound. The dispersion of PTFE and the agglomerate particle sizes were also estimated using SEM.

3. RESULTS AND DISCUSSION

3.1 Swelling Analysis of NR/NBR/PTFE Blend With and Without ZnO

Figures 1 to 3 show the graphs of the effect of solvents (acetone, heptane and toluene respectively) on the mass of rubber compound, blended with and without ZnO. The amounts of ZnO used varied from 0, 3, 5 to 8 phr based on the requirement for rubber formulations. It can be seen that after 23 hours of immersion, the mass of rubber samples increased as the immersion hours increased. The 3 phr ZnO added in the rubber blends did not show any significant change in the rubber swelling, as the change in the mass of the rubber samples showed a similar trend to the rubber blend without ZnO. However, an increase from 5 to 8 phr of ZnO added to the rubber blend significantly reduced the rubber swelling. It is presumed that the addition of ZnO contributes to the enhancement of PTFE dispersion and homogeneity in the rubber matrices. The PTFE agglomerates reduced in sizes during the shear mixing with ZnO thus allowing a high surface area of agglomerates to be dispersed throughout the rubber matrices. The better dispersion of PTFE in the rubber matrices with fine particle sizes allow a homogenized blend in the rubber, hence better resistance of the rubber to solvents could be achieved.

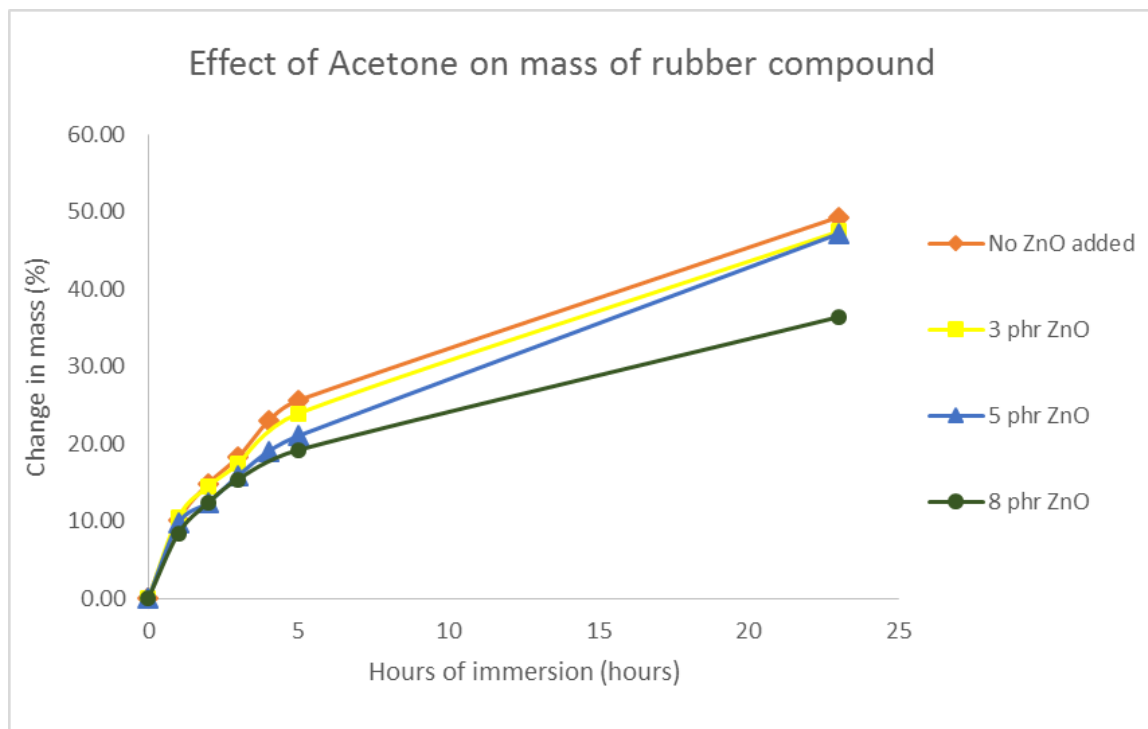


Figure 1: Effect of Acetone on the mass of rubber compound.

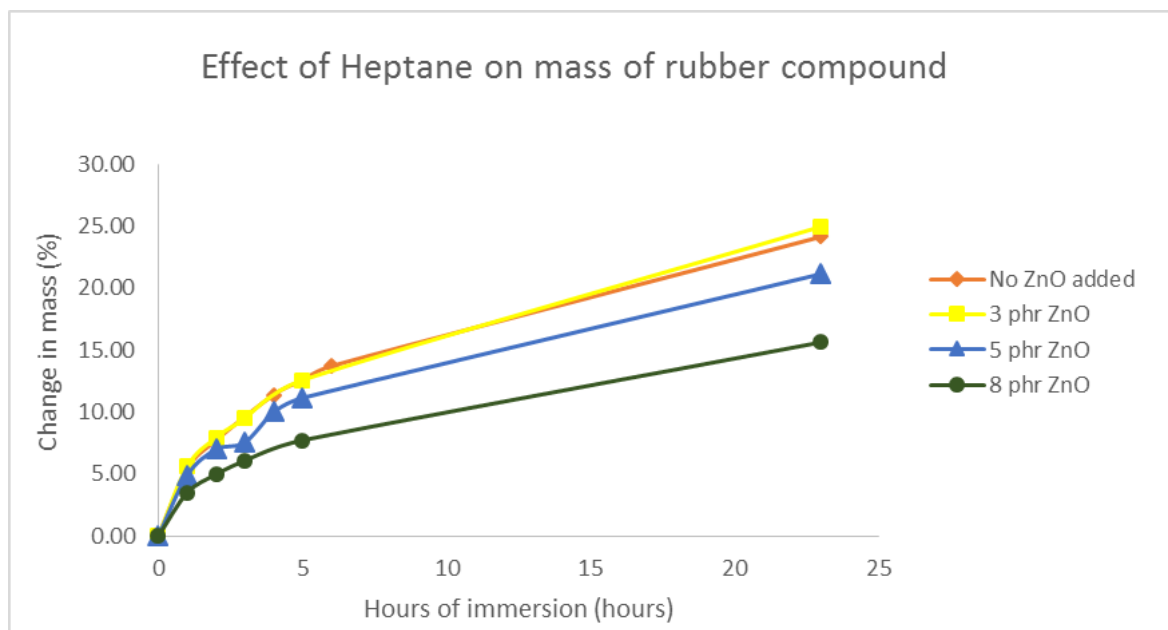


Figure 2: Effect of Heptane on the mass of rubber compound.

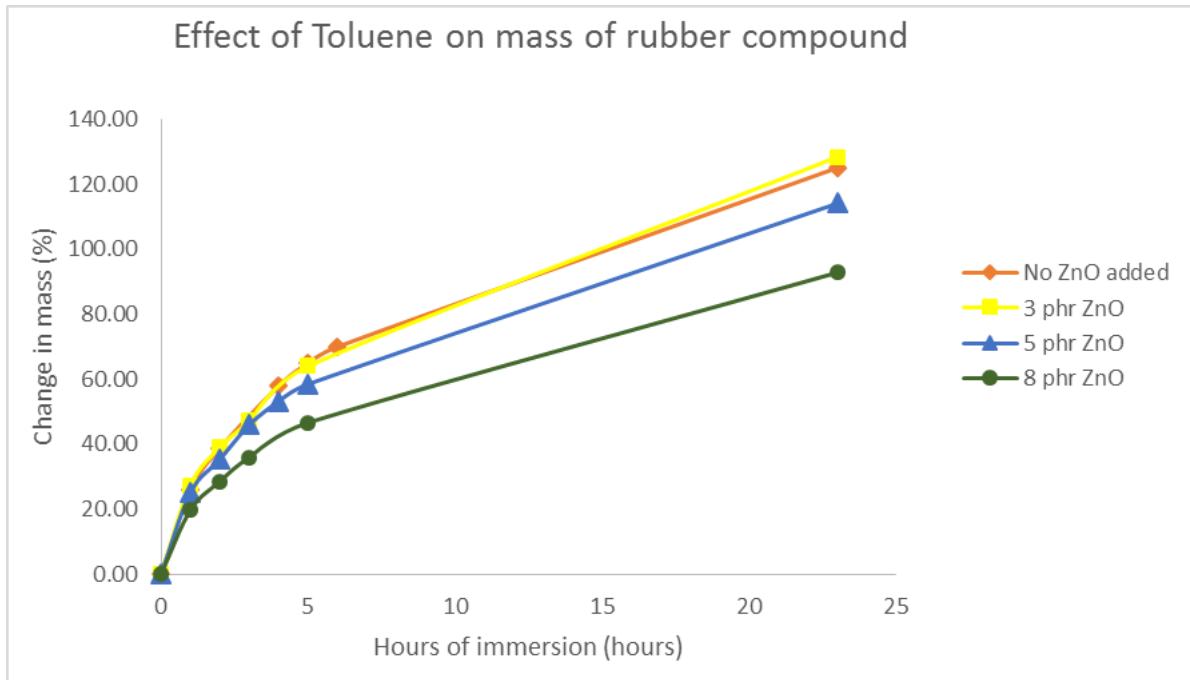


Figure 3: Effect of Toluene on the mass of rubber compound.

3.2 Microstructural Analysis by SEM/EDX

To further support the findings, the SEM analysis of the PTFE-filled rubber was performed to determine the homogeneity of PTFE in rubber matrix blended with and without ZnO. Figure 4 shows the SEM micrographs of overall rubber surfaces of the NR/NBR/ PTFE rubber blend without ZnO (sample 1). The diagram shows few agglomerations of PTFE along with rubber lumps found on the rubber surface with particles sizes varying considerably. A further enhanced image was made at a magnification of 2kX to estimate the average of large PTFE particle sizes. It was found that the average of large PTFE agglomerates was in the order of 6-22 μm as shown in Figure 5.

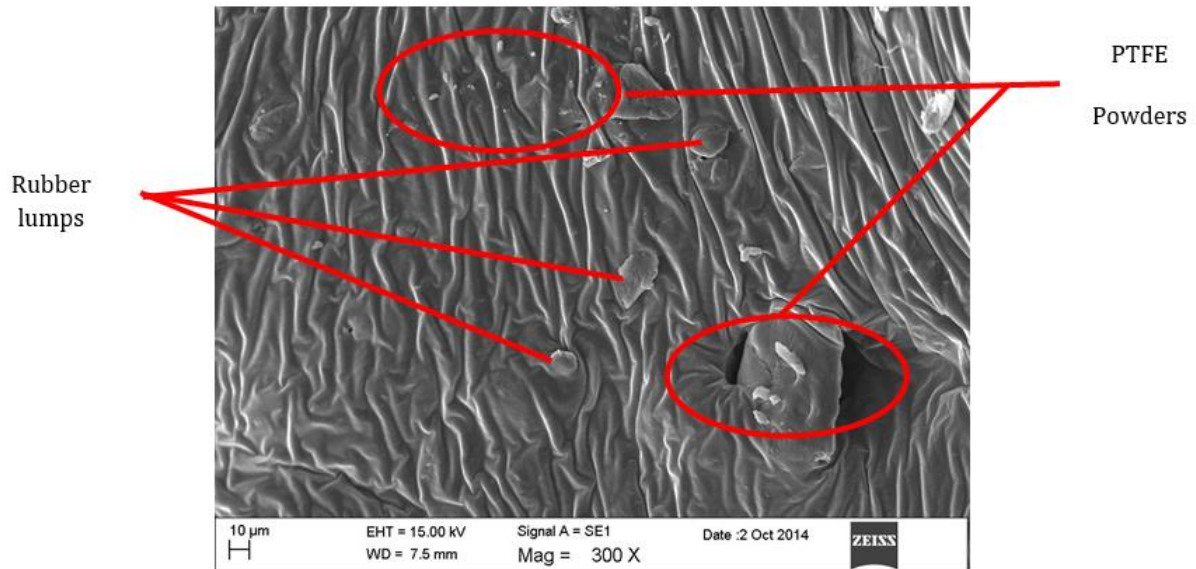


Figure 4: The PTFE powders in the rubber blend without ZnO.

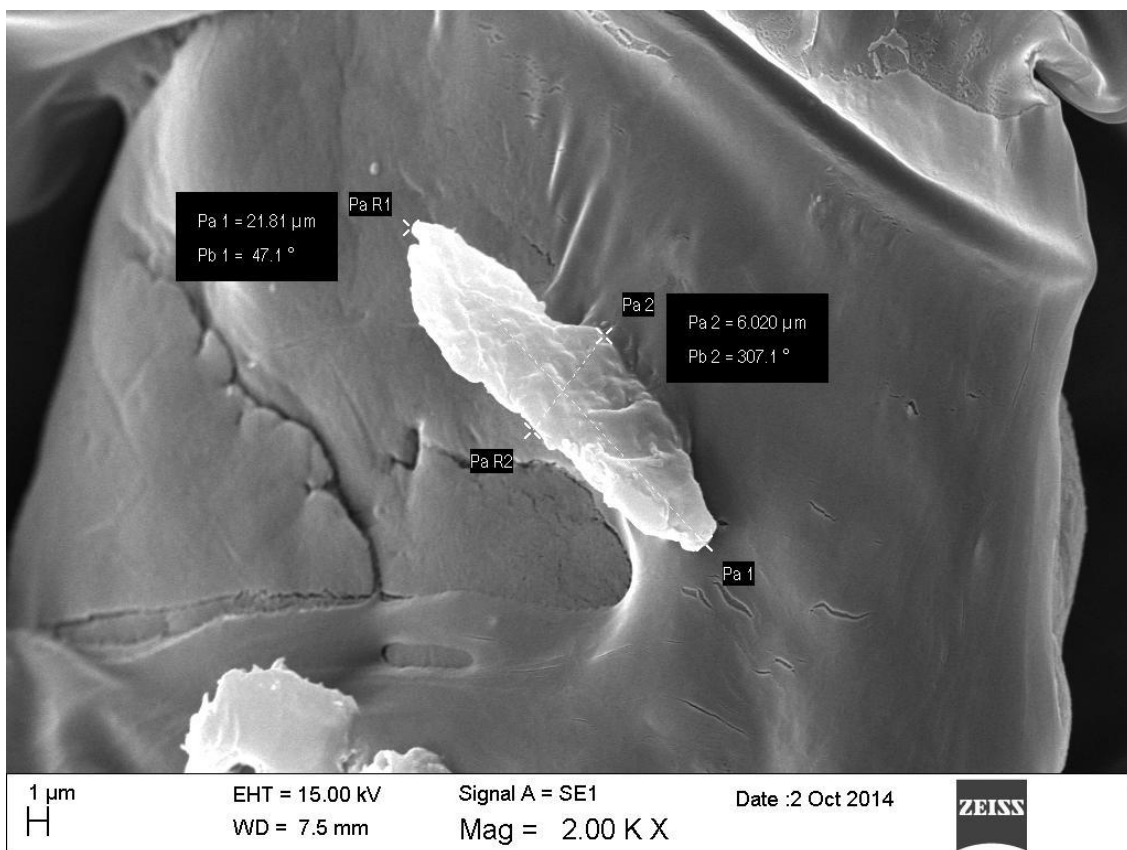


Figure 5: The average particle sizes of large PTFE particle.

Meanwhile, for the PTFE-filled rubber blend with 8 phr ZnO, the overall view of the rubber surfaces by SEM at the same magnification as in Figure 4 shows that there was less agglomerations of PTFE found on the rubber surface and the sizes of the agglomerate particles had reduced. The largest agglomerates of PTFE could only be found at a higher

magnification of 2kX and the average of this particle size of PTFE was in the order of 2-8 μm (Figure 6 – Right).

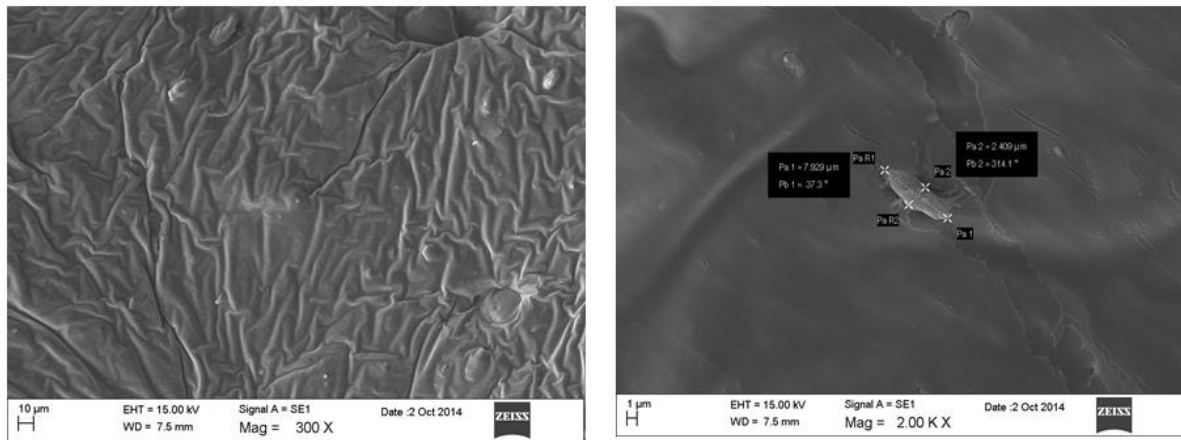


Figure 6: (Left) The PTFE powders in rubber blended with ZnO, (Right) The average particle size of large PTFE powder.

The reduced solvent uptake by the blend of the rubber is due to the presence of ZnO during rubber mixing with PTFE which helped to increase the dispersion of PTFE in rubber matrices. ZnO is an activator in rubber compounding normally used in small proportion to increase the effectiveness of accelerators (Nagdi, 1993). The presence of ZnO during PTFE blending could activate the carboxylic acid group in the PTFE to combine with rubber matrices (Khan et al., 2009a), hence enhanced dispersion can be achieved. The SEM-EDX image in Figure 7 shows that the ZnO element disperses uniformly in the rubber matrices as well as the fluorine element (represents the PTFE micropowder) which also uniformly disperses in the rubber. Consequently, the addition of ZnO during rubber blending reduces the PTFE agglomerates and increases the surface area of PTFE, hence reduced solvent uptake by the rubber could be achieved.

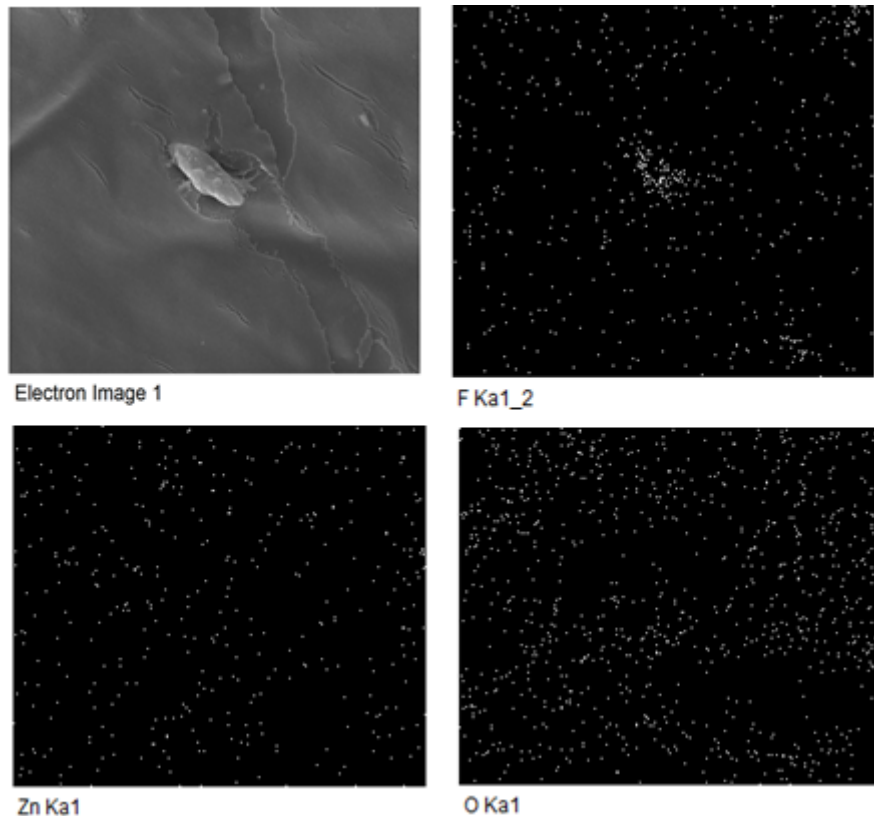


Figure 7: The SEM-EDX analysis of PTFE rubber blend with 8 phr ZnO a) Top-left: The PTFE particle traced by SEM-EDX b) Top-right: Distribution of fluorine element c) Bottom-left: Distribution of Zn element d) Bottom-right: Distribution of Oxygen element.

4. CONCLUSION

The effect of ZnO on the dispersion and homogeneity of PTFE micropowder in NR/NBR rubber matrices has been investigated. The findings from the rubber swelling analysis show that the PTFE-filled rubber blend with 8 phr ZnO shows an improvement in the resistance towards solvents. Further investigations on the microstructural image of the rubber compound blend with ZnO shows that the PTFE agglomerates reduced in sizes and were found to have enhanced dispersion and homogeneity in the rubber matrices compared to the rubber blend with no ZnO. The mixing of ZnO with PTFE during shear mixing of the rubber compound helps to reduce the PTFE agglomerates. Consequently, a uniformed distribution of the particles could be achieved, resulting in improved resistance towards solvents.

REFERENCES

- Crandell, W. H. (1955). Evaluation of silicone rubber modified with teflon. *Rubber World*, 133, 236-240.
- Drobny, J. G. (2007). Fluoropolymers in automotive applications. *Polymers for Advanced Technologies*, 18, 117-121. doi: 10.1002/pat.807
- Gangal, S. V. (1989). *Tetrafluoroethylene polymers: Encyclopedia of polymer science and engineering*. New York: Wiley.

- Kaufman, M. H., & Gonzales, J. (1968). Reinforcement of fluoropolymers with halopolymers. *Rubber Chemistry and Technology*, 41, 527-532. doi: 10.5254/1.3547189
- Khalaf, A. I., Yehia, A. A., Ismail, M. N., & El-Sabbagh, S. H. (2012). High performance oil resistant rubber. *Open Journal of Organic Polymer Materials*, 2, 88-93. doi: 10.4236/ojopm.2012.24013
- Khan, M. S., Franke R., Lehmann D., & Heinrich G. (2009a). Physical and tribological properties of PTFE micropowder-filled EPDM rubber. *Tribology International*, 42, 890-896. doi: 10.1016/j.triboint.2008.12.014
- Khan, M. S., Lehmann, D., & Heinrich G. (2009b). Newly developed chloroprene rubber composites based on electron-modified polytetrafluoroethylene powder. *Acta Materialia*, 57, 4882-4890. doi:10.1016/j.actamat.2009.06.043
- Lahijani, J. (2003). Melt-fabricable polytetrafluoroethylene. *US Patent No. 6265492*. Washington, DC: U.S. Patent and Trademark Office.
- Lee, B. L., Patel, R., Cox, M., & Andries, J. C. (2005). Polyvinyl chloride or polyolefin melt processible compositions containing polytetrafluoroethylene micropowder. *US Patent No. 6977280*. Washington, DC: U.S. Patent and Trademark Office.
- Morgan, R. A., Stewart, C. W., Thomas, E. W., & Stahl, W. M. (1991). Reinforcement with fluoroplastic additives. *Rubber World*, 204(2), 236-240.
- Nagdi, K. (1993). *Rubber as an engineering material: Guideline for users*. Germany: Hanser.
- Stachowiak, G. W., & Batchelor, A. W. (1993). Preface. In G. W. Stachowiak & A. W. Batchelor (Eds.), *Tribology Series 24*, (pp. 4). Netherlands: Elsevier. doi: 10.1016/S0167-8922(08)70573-X